

|                                                                                                                                                                                                                                                                 |                                                                                                 |
|-----------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------|-------------------------------------------------------------------------------------------------|
|                                                                                                                                                                                |              |
| <p>© Article authors. This is an open access article distributed under the Creative Commons Attribution-NonCommercial-NoDerivs licens. (<a href="http://creativecommons.org/licenses/by-nc-nd/3.0/">http://creativecommons.org/licenses/by-nc-nd/3.0/</a>).</p> | <p>ISSN online 2545-2819<br/>ISSN print 0800-6377</p>                                           |
| <p>DOI: 10.2478/ncr-2025-0005</p>                                                                                                                                                                                                                               | <p>Received: Feb. 17, 2025<br/>Revision received: June 19, 2025<br/>Accepted: June 21, 2025</p> |

## Assessing Climate Change Effects on Freeze-Thaw Exposure of Concrete Structures



Toni Pakkala, D.Sc  
University Lecturer  
P.O. Box 600, FI-33014, Tampere University, Finland  
toni.pakkala@tuni.fi



Niko Lindman, M.Sc  
Doctoral Researcher  
P.O. Box 600, FI-33014, Tampere University, Finland  
niko.lindman@tuni.fi



Jukka Lahdensivu, D.Sc  
Research Manager  
P.O. Box 600, FI-33014, Tampere University, Finland  
jukka.lahdensivu@tuni.fi

## ABSTRACT

This study presents a novel method to assess the freeze-thaw exposure of concrete structures. The new Relative Freeze-Thaw Exposure index (RFE) is based on regression model that considers location-related actual freeze-thaw damage observations, number of freeze-thaw cycles and both annual and cycle-related amount of wind-driven rain (WDR) before cycles. The RFE index is then used to compare location-, direction- and climate-related freeze-thaw exposure levels.

It can be concluded that the amount of WDR before each cycle has the most significant effect on freeze-thaw damage. Freeze-thaw exposure level is highest in present climate and remains the highest in Finland's coastal area regardless of the used climate change scenario. In Finland's coastal area and southern Finland, the exposure level increases more from eastern and western directions than southern which indicates that the exposure level is getting more evenly distributed. However, the southern direction remains with the most severe exposure in almost every studied case in every location.

Freeze-thaw exposure for outdoor concrete structures is not getting less severe with the changing climate in Finland. The quality of concrete (e.g. success of air-entrainment) and protecting concrete from free water remain the main methods against the initiation of freeze-thaw damage.

**Key words:** concrete structure, freeze-thaw damage, wind driven rain, durability, climate change

## 1. INTRODUCTION

Freeze-thaw damage is one of the two major degradation mechanisms of climate exposed concrete structures in existing Finnish building stock, the other being carbonation induced corrosion [1]. In recent studies [2 - 4], it has been shown that the amount of wind-driven rain (WDR) before freeze-thaw cycles has a major effect on the rate of freeze-thaw damage. Based on a comprehensive condition investigation data [5], Lahdensivu [1] and Pakkala et al. [2] have presented that in Finland it has taken considerably fewer freeze-thaw cycles after rain or sleet events for incipient damage to occur in coastal area than in the inland. The numbers were 307 and 388 cycles, respectively, when the limit temperature was set to -5°C. In 1980 - 2009 climate conditions the numbers corresponded to 26 and 37 years, respectively, to incipient freeze-thaw damage to occur.

Pakkala et al. [3] presented that far-advanced freeze-thaw damage is strongly related to the amount of freeze-thaw cycles after rain or sleet events. In addition to location-related differences in far-advanced freeze-thaw damage, the observed damage is strongly related to the direction of WDR. Over 80% of far-advanced freeze-thaw damage observed in condition investigations has been concentrated on west to south-east directions, so is the share of WDR. The share of both the freeze-thaw damage and WDR is even more concentrated in mentioned directions in the coastal area than in the inland.

Freeze-thaw damage needs both the free water in the concrete pore system and freeze-thaw cycles to occur. Thus, the main stress factors are the number of cycles and the amount of water inside the concrete pores, mainly provided by WDR. Even though the relation between observed damage and the mentioned stress factors has been shown, the relevance of each component is yet

somewhat unclear. There are no clear methods to estimate the severity of a freeze-thaw load. Lisø et al. [6] presented a combination of frost decay exposure index (FDEI) and freezing point crossings (FPC) to characterise the risk of freeze-thaw damage to a porous, mineral based materials in a given climate. In their studies, the freeze-thaw cycles were considered as temperature crossings over freezing point ( $0^{\circ}\text{C}$ ) and the number of cycles was defined as annual average number of days with freezing point crossings. The FDEI links FPC to the amount of liquid precipitation recorded from the day an FPC has occurred and the preceding two, three or four days. When the FDEI and FPC are shown in the same diagram, the risk of frost decay can be estimated by analysing their relation. However, Pakkala et al. [2] and Pakkala [4] presented a few problems with the studies: the actual freezing point temperature in concrete pore structure is lower,  $<-5^{\circ}\text{C}$  depending on pore size [7], and freezing point crossings should be calculated after a rain event to assess the events when there is possible free water in the concrete pore system.

Based on measurements in Finland, Pakkala [4] has presented the number of freeze-thaw cycles with a limit temperature of  $-5^{\circ}\text{C}$ , the average annual amount of the rain and sleet maximum of 72 hours before the cycles and the average amount of WDR maximum of 72 hours before a cycle. The calculations were made in 1980 - 2009 climate and projected to 2050 (2035 - 2064) and 2100 (2085 - 2114) climates, in four different locations and from different directions based on the wind direction during the rain event. The future climate projections were based on IPCC SRES A2 scenario [8]. The conclusion was that based on the used scenario, the number of freeze-thaw cycles is decreasing in all studied locations except the northernmost part of the country (Lapland). Based on the studied scenarios, the average annual amount of WDR before freeze-thaw cycles is decreasing in the coastal area and in southern Finland but increasing in other locations. The average amount of WDR before a cycle, considered as an intensity of the freeze-thaw load, is decreasing only mildly in the coastal area and increasing in every other location. In all the studied cases, the coastal area is the most loaded area. In future climate projections, the load level in inland locations is approaching the present level in coastal area.

Pakkala et al. [2, 9] and Pakkala [4] have assessed in former studies the effect of climate change on the freeze-thaw load on Finnish concrete facades and balconies. The studies were made based on IPCC 2007 [8] climate models and more precisely on a single scenario A2. Pakkala concluded [4] that one of the main needs for further research is to study both updated and other scenarios. The latter need is based on the assumption that if the projected  $\text{CO}_2$  level is lower than in scenario A2, the number of freeze-thaw cycles might not decrease with such rate. In addition, it was concluded that more focus should be aimed to estimate the severity of the freeze-thaw load, i.e., to compare the number of freeze-thaw cycles after rain events, amount of annual WDR before freeze-thaw cycles and the amount of WDR before of a freeze-thaw cycle.

One third of the floor area of Finnish building stock is block of flats of which the major part is concrete buildings. A major part of it is now aged between 30 to 60 years. In addition, Lahdensivu [1] and Pakkala et al. [2] have shown that even though concrete buildings built according to current Concrete Codes are freeze-thaw durable, yet the actual quality of the concrete may not have reached the requirements. Thus, it is important to study the upcoming climate conditions for assessing the buildings' possible service life and as a groundwork for their maintenance programs and estimations of their possible repair costs in the future.

The research objective was to study how to assess the severity of freeze-thaw load in future climate in different locations in Finland. The results can be used also for other porous mineral-based materials with similar freeze-thaw damage mechanism such as bricks, mortars, and rendering. In this research, the climate change effect on freeze-thaw damage is studied by using

updated climate change scenarios (Representative Concentration Pathways, RCPs) produced by Finnish Meteorological Institute (FMI) in a RASMI-project [10].

## 2. MATERIALS AND METHODS

### 2.1 Condition investigation database

The research material consists of the database collected by Tampere University and Ramboll Finland Oy, which includes condition investigation reports of concrete facades and thin-section analyses of concrete drill samples taken in connection with these investigations. The buildings in the utilised data were constructed between the years 1963 and 1995 and were on average 25 years old at the time of the condition investigation (min = 7 years, max = 49 years, standard deviation = 8 years). Facade condition investigation reports have been conducted in accordance with the Finnish condition investigation guideline [11]. The thin-section analyses have been performed in accordance with standard ASTM C856/C856M - 20 [12].

Since freeze-thaw damage observations in reports of the thin-section analyses have been expressed in verbal form, they have been converted into numerical values for the calculations. This conversion procedure is based on the system presented by Koskiahde [13], see Table 1. In this article, only those samples showing incipient to widespread freeze-thaw damage have been used (n = 325, damage class 2 - 4). In the initial data, concrete drill samples have been reported with precision for main and intermediate compass directions. In this article, the sampling directions have been adjusted to correspond only to the main compass directions in a way that samples taken from intermediate compass directions have been evenly distributed under adjacent main compass directions.

*Table 1 – Classification of freeze-thaw damage indicating cracking observations [13]*

| Class | Freeze-thaw damage indicating cracking                                                                                                                                                                                                    |
|-------|-------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------|
| 1     | No sign of cracks due to freeze-thaw damage.                                                                                                                                                                                              |
| 2     | Initial freeze-thaw cracking. Sporadic microcracks observed, typically <0.01mm in width and <10mm in length. No cracks exceeding 0.1mm in width and 25mm in length allowed.                                                               |
| 3     | Frequent freeze-thaw cracking. Crack pattern commonly parallel to the surface. Typical crack widths 0.01 - 0.1mm and lengths ≥10mm. Incidence <0.25 cracks/mm and <50% of paste-aggregate (coarse-grained aggregate) interfaces detached. |
| 4     | Severe freeze-thaw cracking. Several cracks >0.1mm in width and >25mm in length. Incidence ≥0.25 cracks/mm or ≥50% of paste-aggregate interfaces detached.                                                                                |

Finland is divided in four geographical areas based on both the climatic conditions and the population distribution: coastal area, southern Finland, inland and Lapland. The division and its fundamentals are presented more precisely in Pakkala [4, pp. 17 - 18]. The database includes investigated buildings widely throughout Finland except for Lapland area. Only one investigated building located in Lapland, so the observations are included in the Inland data.

### 2.2 Estimating freeze-thaw load

The level of freeze-thaw load for vertical structures is estimated based on three different indices:

- Freezing Point Crossings (FPC): the number of freeze-thaw cycles with limit temperature  $-5^{\circ}\text{C}$  and maximum of 72 hours after precipitation event.
- Annual Freeze-Thaw Exposure (AFTE): the average annual amount of WDR maximum of 72 hours before the FPC.
- Intensity of the Freeze-Thaw Exposure (IFTE): the average amount of WDR maximum of 72 hours before an FPC.

The precipitation event in all indices is considered to be precipitation in the form of rain or sleet. It is delimited from the climate data by considering precipitation only when temperature is  $\geq 0^{\circ}\text{C}$ . For modelling WDR, i.e., precipitation on vertical surface, a standardised airfield annual index  $I_A$  [14] is used. It gives an estimation of the amount of precipitation on vertical surfaces from different directions at a height of 10 m above ground level at an open place (in the middle of the airfield). The  $I_A$  [14] can be calculated with the following Equation 1:

$$I_A = \frac{2}{9} \frac{\sum_{N} v r^{\frac{8}{9}} \cos(D-\theta)}{N} \quad (1)$$

where,  $v$  is hourly mean wind speed [m/s],  $r$  is hourly total rainfall [mm],  $D$  is hourly mean wind direction from north [ $^{\circ}$ ],  $\theta$  is wall orientation relative to north [ $^{\circ}$ ],  $N$  is the number of years for which data is available, and the summation is taken over all hours for which  $\cos(D - \theta)$  is positive.

In AFTE index the airfield annual index is used as it is presented above but only for the cases where there is a FPC during following 72 hours. Thus, in  $I_A^{AFTE}$  the  $N$  in Equation 1 is 30 years. In IFTE index every FPC and the amount of WDR during preceding 72 hours is considered to be a unique case so that an average of every such case in the 30-year data is calculated. Thus, the Equation 1 is modified as follows:

$$I_A^{IFTE} = \frac{2}{9} \frac{\sum v r^{\frac{8}{9}} \cos(D-\theta)}{N_C} \quad (2)$$

where,  $N_C$  is total number of cases during the 30-year data.

### 2.3 Climate data

Finland is divided in four geographical areas based on both the climatic conditions and the population distribution. The division and its fundamentals are presented more precisely in Pakkala [4, pp. 17 - 18]. The geographical areas and the weather stations (with their geographical coordinates) representing them are:

- Coastal area, Helsinki-Vantaa airport (60.31,24.97)
- Southern Finland, Jokioinen observatory (60.81,23.50)
- Inland, Jyväskylä airport (62.40,25.67)
- Lapland (northern Finland), Sodankylä observatory (67.37,26.63).

The FMI [10] has produced climate data for those four locations in present and projected future climates for the time series 2050 and 2080. The time series representing future climate were compiled for three Representative Concentration Pathways (RCP):

- RCP2.6 representing small greenhouse-gas emissions.
- RCP4.5 representing medium greenhouse-gas emissions.
- RCP8.5 representing very large greenhouse-gas emissions.

The climate data of the weather stations representing present climate are collected every three hours between 1989 and 2018. The three-hour data linearly interpolated as an hourly data. The data used in this study consist of the following variables: temperature, relative humidity, wind speed and direction and precipitation. The hourly projections of the same variables are made for two future 30-year time periods: 2050 (2035 - 2064) and 2080 (2065 - 2094). The projections were made for all studied locations and scenarios.

The variables used in this study are presented in the data with the following accuracy:

- temperature: 0.01°C
- wind speed: 0.01 m/s
- wind direction: 0.1°
- precipitation: 0.01 mm.

Pakkala [15] has presented earlier the following numbers:

- The average annual number of FPC's with limit temperature -5°C and maximum of 72 hours after precipitation event in present and future climate projections.
- The average annual amount of WDR before freeze-thaw cycles,  $I_A^{AFTE}$ , in present and future climates and in different locations.
- The average amount of WDR before each freeze-thaw cycle,  $I_A^{IFTE}$ , in present and future climates and in different locations.

In Table 2, the numbers in present climate are converted as relative numerical values for the purpose of generating regression model presented in Section 2.4. As mentioned before, the observed freeze-thaw deterioration rate has been the greatest in southern facades in every studied location. Thus, to represent present climate, the relative number 100 is the number of FPC's after precipitation events and the amount of  $I_A^{AFTE}$ , and  $I_A^{IFTE}$  from southern directions. Lapland is excluded due to the lack of condition investigation data (see Section 2.1).

*Table 2 – Created relative numerical values for each location and facing direction*

| Location  | Direction | Relative number of FPC's | Relative amount of $I_A^{AFTE}$ | Relative amount of $I_A^{IFTE}$ |
|-----------|-----------|--------------------------|---------------------------------|---------------------------------|
| Vantaa    | North     | 74                       | 14                              | 20                              |
|           | East      | 59                       | 25                              | 43                              |
|           | South     | 100                      | 100                             | 100                             |
|           | West      | 105                      | 49                              | 47                              |
| Jokioinen | North     | 70                       | 15                              | 22                              |
|           | East      | 50                       | 26                              | 53                              |
|           | South     | 100                      | 100                             | 100                             |
|           | West      | 109                      | 60                              | 55                              |
| Jyväskylä | North     | 80                       | 36                              | 45                              |
|           | East      | 72                       | 41                              | 57                              |
|           | South     | 100                      | 100                             | 100                             |
|           | West      | 106                      | 62                              | 59                              |

For the purpose to compare regression model-based freeze-thaw load level in different locations and climates and variously oriented facades, Tables 3 - 5 represent the relative number of FPC's and relative amount of  $I_A^{AFTE}$ , and  $I_A^{IFTE}$ , respectively, related to the coastal area southern facade (relative reference level: 100). The employed unitless reference value of 100 has been chosen arbitrarily, but it serves as a practical value for comparing the varying degrees of freeze-thaw load across different locations and facade orientations.

*Table 3 – The relative number of FPC's on different locations, facing directions and studied climates. Relative reference level 100 is set to represent southern facade conditions in coastal area in present climate.*

| Location         | Direction | Used climate data |        |        |        |        |        |        |
|------------------|-----------|-------------------|--------|--------|--------|--------|--------|--------|
|                  |           | Present           | 2050   |        |        | 2080   |        |        |
|                  |           |                   | RCP2.6 | RCP4.5 | RCP8.5 | RCP2.6 | RCP4.5 | RCP8.5 |
| Coastal area     | North     | 74                | 79     | 78     | 77     | 77     | 75     | 58     |
|                  | East      | 59                | 64     | 62     | 61     | 62     | 58     | 48     |
|                  | South     | 100               | 93     | 85     | 77     | 90     | 74     | 46     |
|                  | West      | 105               | 97     | 90     | 77     | 95     | 80     | 45     |
| Southern Finland | North     | 84                | 96     | 92     | 83     | 96     | 79     | 100    |
|                  | East      | 59                | 65     | 64     | 62     | 65     | 60     | 76     |
|                  | South     | 119               | 111    | 105    | 94     | 112    | 92     | 95     |
|                  | West      | 130               | 118    | 111    | 95     | 117    | 90     | 103    |
| Inland           | North     | 106               | 111    | 116    | 120    | 110    | 117    | 103    |
|                  | East      | 95                | 92     | 93     | 94     | 93     | 90     | 76     |
|                  | South     | 133               | 134    | 133    | 132    | 132    | 127    | 92     |
|                  | West      | 140               | 143    | 142    | 141    | 142    | 137    | 107    |
| Lapland          | North     | 84                | 103    | 116    | 124    | 105    | 123    | 151    |
|                  | East      | 84                | 103    | 113    | 120    | 104    | 120    | 140    |
|                  | South     | 129               | 145    | 161    | 159    | 146    | 162    | 168    |
|                  | West      | 133               | 155    | 170    | 171    | 157    | 170    | 181    |

*Table 4 - The relative number of  $I_A^{AFTE}$  on different locations, facing directions and studied climates. Relative reference level 100 is set to represent southern facade conditions in coastal area in present climate.*

| Location         | Direction | Used climate data |        |        |        |        |        |        |
|------------------|-----------|-------------------|--------|--------|--------|--------|--------|--------|
|                  |           | Present           | 2050   |        |        | 2080   |        |        |
|                  |           |                   | RCP2.6 | RCP4.5 | RCP8.5 | RCP2.6 | RCP4.5 | RCP8.5 |
| Coastal area     | North     | 14                | 21     | 20     | 21     | 21     | 20     | 21     |
|                  | East      | 25                | 34     | 37     | 31     | 35     | 30     | 31     |
|                  | South     | 100               | 93     | 92     | 72     | 91     | 67     | 31     |
|                  | West      | 49                | 45     | 44     | 37     | 44     | 35     | 19     |
| Southern Finland | North     | 11                | 14     | 16     | 17     | 14     | 16     | 21     |
|                  | East      | 19                | 20     | 23     | 26     | 21     | 26     | 26     |
|                  | South     | 72                | 64     | 60     | 55     | 64     | 53     | 43     |
|                  | West      | 44                | 41     | 42     | 36     | 41     | 35     | 30     |
| Inland           | North     | 19                | 18     | 23     | 24     | 18     | 24     | 28     |
|                  | East      | 21                | 26     | 31     | 31     | 26     | 30     | 29     |
|                  | South     | 52                | 54     | 59     | 57     | 55     | 56     | 49     |
|                  | West      | 33                | 32     | 35     | 35     | 32     | 34     | 33     |
| Lapland          | North     | 13                | 15     | 19     | 21     | 16     | 21     | 29     |
|                  | East      | 18                | 23     | 26     | 29     | 24     | 30     | 42     |
|                  | South     | 43                | 51     | 59     | 64     | 52     | 65     | 71     |
|                  | West      | 19                | 24     | 28     | 40     | 24     | 30     | 34     |

*Table 5 - The relative number of  $I_A^{IFTE}$  on different locations, facing directions and studied climates. Relative reference level 100 is set to represent southern facade conditions in coastal area in present climate.*

| Location         | Direction | Used climate data |        |        |        |        |        |        |
|------------------|-----------|-------------------|--------|--------|--------|--------|--------|--------|
|                  |           | Present           | 2050   |        |        | 2080   |        |        |
|                  |           |                   | RCP2.6 | RCP4.5 | RCP8.5 | RCP2.6 | RCP4.5 | RCP8.5 |
| Coastal area     | North     | 20                | 27     | 26     | 27     | 27     | 27     | 36     |
|                  | East      | 43                | 53     | 60     | 51     | 56     | 52     | 65     |
|                  | South     | 100               | 100    | 107    | 93     | 101    | 91     | 67     |
|                  | West      | 47                | 46     | 48     | 44     | 46     | 44     | 43     |
| Southern Finland | North     | 13                | 15     | 18     | 20     | 15     | 20     | 21     |
|                  | East      | 32                | 32     | 37     | 42     | 32     | 43     | 34     |
|                  | South     | 61                | 57     | 57     | 58     | 57     | 58     | 45     |
|                  | West      | 34                | 35     | 38     | 38     | 35     | 39     | 29     |
| Inland           | North     | 18                | 16     | 19     | 20     | 16     | 20     | 27     |
|                  | East      | 22                | 28     | 33     | 33     | 28     | 33     | 38     |
|                  | South     | 39                | 41     | 44     | 43     | 42     | 44     | 53     |
|                  | West      | 23                | 22     | 25     | 25     | 23     | 25     | 31     |
| Lapland          | North     | 16                | 15     | 16     | 17     | 15     | 17     | 19     |
|                  | East      | 22                | 22     | 23     | 24     | 23     | 25     | 30     |
|                  | South     | 34                | 35     | 37     | 40     | 35     | 40     | 42     |
|                  | West      | 14                | 15     | 17     | 18     | 15     | 18     | 19     |

## 2.4 Multilinear regression model

As mentioned in Chapter 1, there is no comprehensive methods to combine all earlier mentioned factors of freeze-thaw exposure and thus, no methods to assess the severity of exposure so that every factor is considered. To formulate a relative method to combine the factors, a Relative Freeze-Thaw Exposure (RFE) index is created. To calculate RFE index, a multilinear regression was used utilising FPC,  $I_A^{AFTE}$ , and  $I_A^{IFTE}$  indices (see Section 2.2) and the collected far-advanced freeze-thaw damage data (see Section 2.1).

To create the multilinear regression model, location related relative FPC,  $I_A^{AFTE}$ ,  $I_A^{IFTE}$ , and far-advanced freeze-thaw damage data were created, see Table 2 and Section 3.1. The relative reference level (100) is set individually in each of the locations because the share of the far-advanced freeze-thaw damage on different direction facing facades was location related. Each of the factor used to create the model were cross tabulated in regression calculations. The regression was calculated according to Equation 3.

$$RFE = \beta_0 + \beta_1 x_1 + \beta_2 x_2 + \beta_3 x_3 \quad (3)$$

where,  $\beta_0$  is interception term,  $\beta_1 x_1$  coefficient of independent variable 1 (FPC parameter),  $\beta_2 x_2$  coefficient of independent variable 2 ( $I_A^{AFTE}$  parameter) and  $\beta_3 x_3$  coefficient of independent variable 3 ( $I_A^{IFTE}$  parameter).

Finally, the model is used to compare freeze-thaw exposure in different locations and climate change scenarios. To compare the exposure level in different locations and climate change scenarios, relative FPC,  $I_A^{AFTE}$ , and  $I_A^{IFTE}$  indices presented in Tables 3 - 5 were used. In this case, the relative reference level was set to be 100 in southern direction in coastal area.



### 3. RESULTS AND DISCUSSION

#### 3.1 Condition investigation data

Table 6 presents freeze-thaw damage observations according to geographical location and the sampling direction. In this study, the observations of freeze-thaw damage are analysed with the accuracy of main compass directions. Since the initial database encompasses both main and intermediate compass directions, the observations from intermediate compass directions are shared in half between the adjacent main compass directions.

*Table 6 - Freeze-thaw damage observations according to geographical location and the sampling direction*

| Location                       | The number of freeze-thaw damage observations | Share [%] |
|--------------------------------|-----------------------------------------------|-----------|
| <b>Coastal area, total</b>     | 199                                           | 100       |
| North                          | 22.5                                          | 11.3      |
| East                           | 48.5                                          | 24.4      |
| South                          | 74.5                                          | 37.4      |
| West                           | 53.5                                          | 26.9      |
| <b>Southern Finland, total</b> | 94                                            | 100       |
| North                          | 15                                            | 16.0      |
| East                           | 25                                            | 26.6      |
| South                          | 36.5                                          | 38.8      |
| West                           | 17.5                                          | 18.6      |
| <b>Inland + Lapland, total</b> | 32                                            | 100       |
| North                          | 4                                             | 12.5      |
| East                           | 9.5                                           | 29.7      |
| South                          | 12                                            | 37.5      |
| West                           | 6.5                                           | 20.3      |
| <b>All locations, total</b>    | 325                                           | 100       |
| North                          | 41.5                                          | 12.8      |
| East                           | 83                                            | 25.5      |
| South                          | 123                                           | 37.8      |
| West                           | 77.5                                          | 23.8      |

Freeze-thaw damage observations seem to appear on the southern facades in all geographical locations, when the least number of damage observations was on the northern facades. In Finland, the geographical location has not been found to have significance on the properties of concretes pore structure, in addition to which various facade surface types have been used evenly across the country [1]. Therefore, the concentration of damage observations in certain directions can be logically explained by climate stress, even though samples are typically taken in relation to the most climate stressed facades during condition investigations.

#### 3.2 Relative freeze-thaw exposure RFE

The used multi-linear regression model was judged by the coefficient of determination ( $R^2$ ) of the model. The  $R^2$  was 0.83 which can be seen as a relatively strong fit. Table 7 shows the parameters and regression coefficients that can be applied in the modelling of the freeze-thaw exposure level. Regression coefficients are used to quantify the relationship between each predictor and the dependent variable (freeze-thaw damage), indicating the direction and strength of their influence. The greater the distance of the regression coefficient from zero, the greater its effect on the dependent variable.

*Table 7 – Regression model for RFE index in concrete facades*

| $R^2$ | $\beta_0$ (intercept) | $\beta_{FPC}$ | $\beta_{I_A^{FTE}}$ | $\beta_{I_A^{FTE}}$ |
|-------|-----------------------|---------------|---------------------|---------------------|
| 0.83  | 8.412                 | -0.045        | -0.134              | 0.471               |

The coefficients indicate that the  $I_A^{FTE}$ , i.e. the intensity of the freeze-thaw exposure, has the highest influence on RFE index and the number of FPC's the lowest.

The relative freeze-thaw exposure index, RFE, from different directions, i.e., on different direction facing vertical structures, is presented in Table 8.

*Table 8 – RFE index in different geographical locations and facade directions*

| Location         | Direction | Used climate data |        |        |        |        |        |        |
|------------------|-----------|-------------------|--------|--------|--------|--------|--------|--------|
|                  |           | Present           | 2050   |        |        | 2080   |        |        |
|                  |           |                   | RCP2.6 | RCP4.5 | RCP8.5 | RCP2.6 | RCP4.5 | RCP8.5 |
| Coastal area     | North     | 12                | 15     | 15     | 15     | 15     | 15     | 20     |
|                  | East      | 23                | 26     | 29     | 26     | 27     | 26     | 33     |
|                  | South     | 38                | 39     | 43     | 39     | 40     | 39     | 34     |
|                  | West      | 19                | 20     | 21     | 21     | 20     | 21     | 24     |
| Southern Finland | North     | 9                 | 9      | 10     | 12     | 9      | 12     | 11     |
|                  | East      | 18                | 18     | 20     | 22     | 18     | 23     | 18     |
|                  | South     | 22                | 22     | 22     | 24     | 22     | 25     | 20     |
|                  | West      | 13                | 14     | 16     | 17     | 14     | 18     | 13     |
| Inland           | North     | 9                 | 9      | 9      | 9      | 9      | 10     | 13     |
|                  | East      | 12                | 14     | 16     | 16     | 14     | 16     | 19     |
|                  | South     | 14                | 14     | 15     | 15     | 15     | 16     | 23     |
|                  | West      | 9                 | 8      | 9      | 9      | 8      | 9      | 14     |
| Lapland          | North     | 10                | 9      | 8      | 8      | 9      | 8      | 7      |
|                  | East      | 12                | 11     | 11     | 10     | 11     | 11     | 11     |
|                  | South     | 13                | 12     | 11     | 12     | 12     | 11     | 11     |
|                  | West      | 7                 | 5      | 5      | 4      | 5      | 5      | 5      |

The RFE index is increasing in coastal area with every scenario and from every direction except 2080 RCP8.5 scenario from southern direction where the scenario decreases considerably. In addition, the RFE index remains the highest in coastal area compared to other studied locations. Only few numbers in other locations exceed the lowest numbers in coastal area, e.g. southern directions in southern Finland and in the inland with 2080 RCP8.5 versus northern direction in coastal area. In southern Finland the RFE index remains, in outline, at present level regardless of the used scenario. In the inland the RFE remains in present level except 2080 RCP4.5 and RCP8.5 scenarios where the increase is notable. Lapland is the only location where the RFE index decreases from every direction and with every scenario compared to present climate.

The inland is the only location where the direction related RFE index scatters compared to present climate, especially with 2080 RCP8.5 scenario. In other locations, the differences between RFE index from different directions remains at present level or even out. In most cases where the RFE index increases, the results indicate that the exposure level on north-facing structures will approach the present level on west-facing structures, level on west-facing structures the present level on east-facing structures and level on east-facing structures the present level on south-facing structures.

The average RFE index in different studied locations are presented in the Table 9 and Figure 1.

Table 9 – RFE index in different geographical locations

| Location         | Used climate data |        |        |        |        |        |        |
|------------------|-------------------|--------|--------|--------|--------|--------|--------|
|                  | Present           | 2050   |        |        | 2080   |        |        |
|                  |                   | RCP2.6 | RCP4.5 | RCP8.5 | RCP2.6 | RCP4.5 | RCP8.5 |
| Coastal area     | 23                | 25     | 27     | 25     | 25     | 25     | 28     |
| Southern Finland | 16                | 16     | 17     | 19     | 16     | 19     | 15     |
| Inland           | 11                | 11     | 12     | 12     | 11     | 13     | 17     |
| Lapland          | 11                | 9      | 9      | 8      | 9      | 9      | 8      |

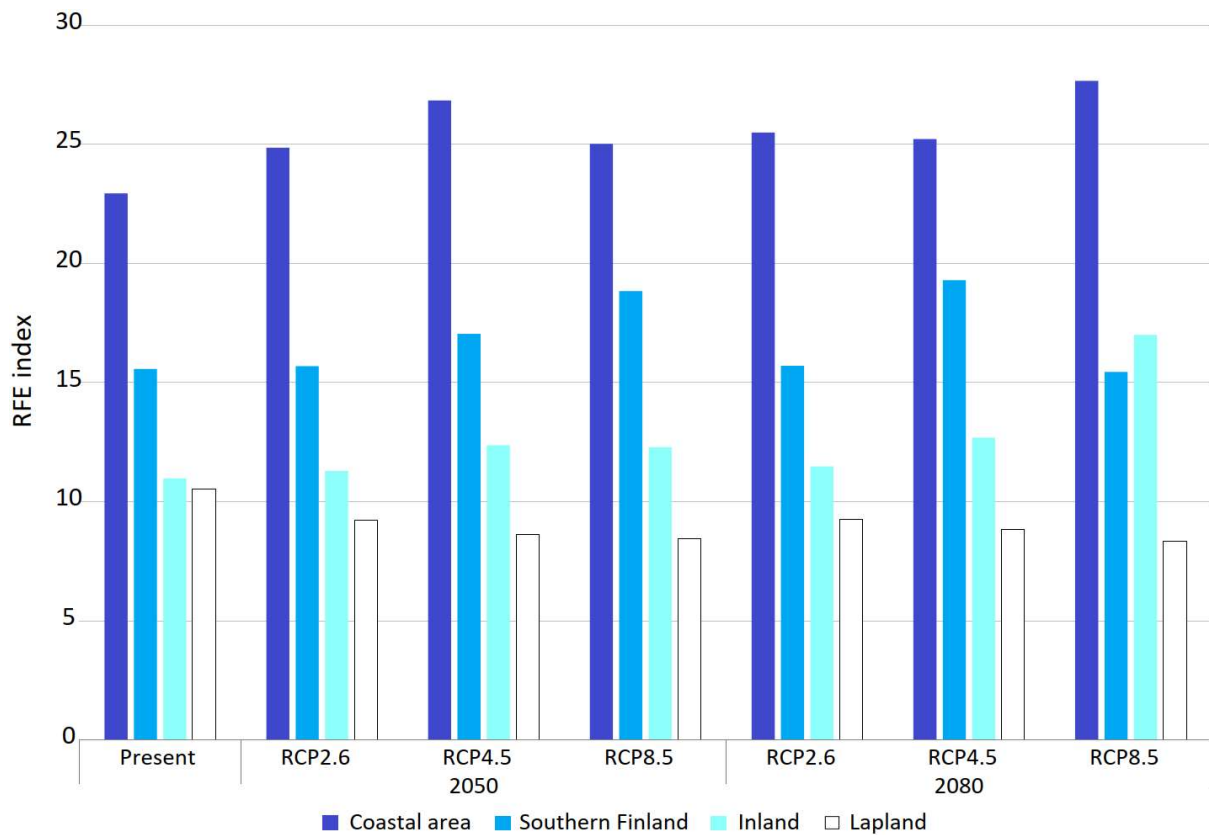


Figure 1 – Average RFE in different geographical locations and climates

Based on the RFE index, the severity of freeze-thaw exposure will be the highest in coastal area regardless of the used scenario. The highest index is with 2080 RCP8.5 scenario in coastal area and the lowest with 2050 and 2080 RCP8.5 scenarios in Lapland. The severity-based order of locations remains the same in every scenario except 2080 RCP8.5 where the inland overtakes southern Finland.

#### 4. CONCLUSIONS

The study presents a novel method to assess the level of freeze-thaw exposure by relative freeze-thaw exposure index, RFE. RFE index is based on regression model that considers:

- Thin-section analyses based on freeze-thaw damage observations in extensive condition investigation database.
- Average annual number of freeze-thaw cycles with limit temperature  $-5^{\circ}\text{C}$ .
- Average annual amount of wet precipitation before the freeze-thaw cycle.
- Average amount of wet precipitation prior to each freeze-thaw cycle.

Each factor is formed separately in four different geographical locations and in each location for four main directions. Finally, RFE index is used to estimate the freeze-thaw exposure between the different locations and directions and to assess the climate change effect to them.

Because the RFE index is based on actual freeze-thaw damage observations in present climate it is the highest in coastal area and from southern direction which have been in former studies shown to be predisposing for the most severe freeze-thaw damage. The results indicate that it will stay the highest regardless of the remarkable decrease in number of FPC's and amount of  $I_A^{AFTE}$  in coastal area with RCP8.5 2080 scenario. The results and calculated coefficients strongly indicate that the amount of  $I_A^{IFTE}$  has the highest significance on freeze-thaw exposure. It highlights the significance of the amount of free water in concrete pore structure prior to freeze-thaw cycle.

The lowest effect of used parameters appears to be the number of FPC's. It correlates with the interpretations made in former studies because the number of FPC's has been the highest in inland and northern Finland even though the freeze-thaw damage observations have been fewer.

Based on the results the following observations can be made:

- Freeze-thaw exposure level remains to be the highest in coastal area regardless of the used scenario and it is increasing with every scenario, in Lapland vice versa.
- In other studied locations, used scenario has more effect on the direction of the exposure level, yet principally remains quite the same level as in present climate.
- The amount of WDR before a freeze-thaw cycle, i.e., the intensity of freeze-thaw exposure, has the highest influence on the exposure level.
- In coastal area and southern Finland, the exposure level increases more from eastern and western directions than southern which indicates that the exposure level is getting more evenly distributed. However, the southern direction remains with the highest RFE in almost every studied case in every location.

As a conclusion it can be drawn that the freeze-thaw exposure for outdoor concrete structures is not getting less severe with the changing climate. Thus, the most important findings are that the quality of concrete (e.g. success of air-entrainment) and protecting concrete from free water remain the main methods against freeze-thaw damage.

The authors acknowledge many sources of error related to the study. E.g., there are far more sophisticated methods to calculate WDR amounts accurately on exact locations, buildings and areas on building facades. However, used method can be seen as an adequate method to compare WDR amounts on general level. In addition, the concrete core sampling is usually focused on the areas known to have the highest exposure level, such as upper parts of southern facades. Also, the surface type and coating of concrete have shown to have an influence on the freeze-thaw durability. However, the database is extensive, and the significance of the mentioned error sources can be seen quite minor when using the data in location and direction-related comparisons.

## 5. ACKNOWLEDGEMENT

The authors would like to thank the researchers at the Finnish Meteorological Institute for preparing the future climate projections. Part of this study is related to research made in the RAMI project in 2021 - 2022 funded by the Finnish Ministry of the Environment and part of the study is

related to research made in on-going (2021 - 2024) BALANCE project funded by Academy of Finland. The researchers would like to thank both funding parties.

## REFERENCES

1. Lahdensivu J: “Durability Properties and Actual Deterioration of Finnish Concrete Facades and Balconies”. Tampere University of Technology, PhD thesis, *TUT Publ.* 1028, 2012, 117 p. <https://urn.fi/URN:ISBN:978-952-15-2823-1>.
2. Pakkala T A, Köliö A, Kiviste M & Lahdensivu J: “Durability demands related to frost attack for Finnish concrete buildings in changing climate”. *Building and Environment*, 82 (2014), 2014, pp. 27–41. <https://doi.org/10.1016/j.buildenv.2014.07.028>.
3. Pakkala T A, Lahdensivu J, Huuhka P, Kivioja H & Lemberg A M: “Freeze-thaw damage dependence on wind-driven rain of outdoor exposed concrete – a case study”. *Nord. Concr. Res.*, 61 (2/2019), 2019, pp. 91 – 106. <https://doi.org/10.2478/ncr-2019-0010>.
4. Pakkala T A: “Assessment of the Climate Change on Finnish Concrete Facades and Balconies”. Tampere University Dissertations 204, Faculty of Built Environment, Tampere, 2020. <https://urn.fi/URN:ISBN:978-952-03-1423-1>.
5. Lahdensivu J, Varjonen S & Köliö A: “Repair Strategies of Concrete Facades”. (“Betonijulkisivujen korjausstrategiat”). Tampere University of Technology, Department of Civil Engineering, *Research report* 148. (in Finnish). <https://urn.fi/URN:NBN:fi:tty-2011041510686>.
6. Lisø K R, Kvande T, Hygen H O, Thue J V & Harstveit K: “A frost decay exposure index for porous, mineral building materials”. *Build. Environ.* 42 (10), pp. 3547 – 3555.
7. Pigeon M, Pleau R: “Durability of concrete in cold climates”. Suffolk. E & FN Spon, 1995, 244 p.
8. IPCC: “Climate Change 2007: The physical science basis”. Contribution of Working Group I to the Fourth Assessment Report of the Intergovernmental Panel on Climate Change, Cambridge University Press, Cambridge, U.K., 2007.
9. Pakkala T A, Lemberg A M, Lahdensivu J & Pentti M: “Climate change effect on wind-driven rain on facades”. *Nord. Concr. Res.* 54 (1/2016), 2016, pp. 31 – 49.
10. Jylhä K, Ruosteenoja K, Böök H, Lindfors A, Pirinen P, Laapas M & Mäkelä A: “Weather data for building-physical studies and the building energy reference year 2020 in a changing climate”. *Reports* 2020:6, updated 9/2021, Finnish Meteorological Institute, 2021. <https://doi.org/10.35614/isbn.9789523361287>.
11. Concrete Association of Finland: “Condition assessment manual of a concrete façade”. (“by 42 - Betonijulkisivun kuntotutkimus”). Vaasa, 2019, 136 p. (in Finnish).
12. ASTM C856-18a: “Standard Practice for Petrographic Examination of Hardened Concrete”. ASTM International, West Conshohocken, PA, 2018, 15 p.
13. Koskiahde A: “An experimental petrographic classification scheme for the condition assessment of concrete in facade panels and balconies”. *Mater. Charact.*, 53 (2004), 2004, pp. 327–334.
14. SFS-EN ISO 15927-3: “Hygrothermal performance of buildings. Calculation and presentation of climatic data. Part 3: Calculation of a driving rain index for vertical surfaces from hourly wind and rain data”. Finnish Standards Association SFS, Helsinki.
15. Pakkala T A: “Climate Change Effect on Freeze-thaw Load in Finland”. *Journal of Physics: Conference Series*, Volume 2654, 13th Nordic Symposium on Building Physics (NSB-2023) 12/06/2023 - 14/06/2023, Aalborg, Denmark. <https://doi.org/10.1088/1742-6596/2654/1/012020>.